


# Diran 410MF07



**FDM Thermoplastic Filament**  
**Perfect for manufacturing**  
**tooling applications.**

The information presented are typical values intended for reference and comparison purposes only.  
They should not be used for design specifications or quality control purposes.

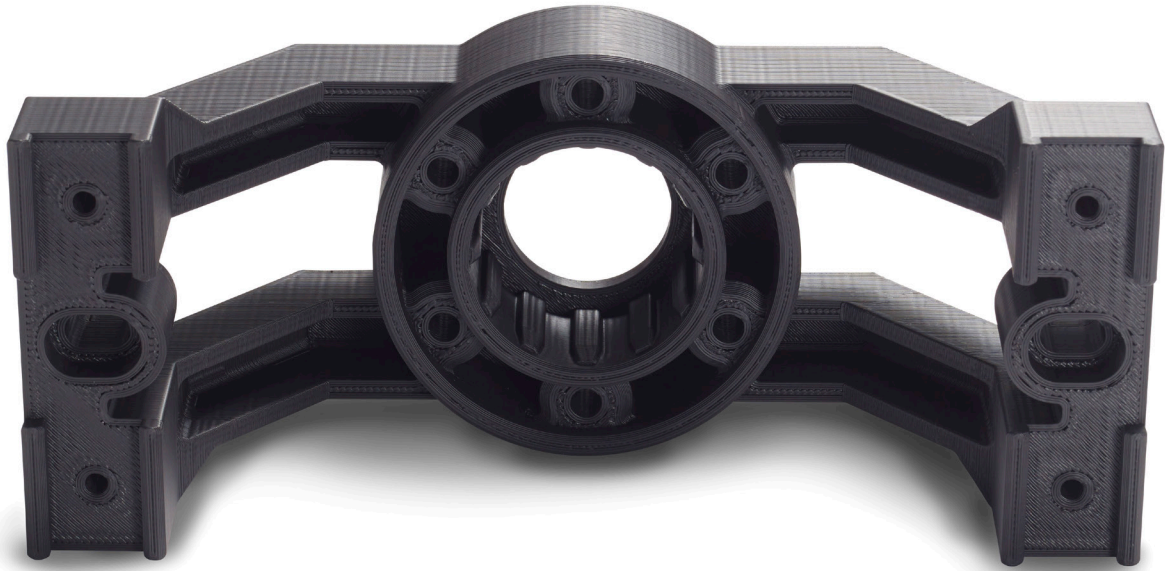

## Overview

Diran™ 410MF07 is a nylon-based thermoplastic FDM® material, mineral-filled 7% by weight. It demonstrates very good toughness and impact strength combined with resistance to hydrocarbon-based chemicals. Its smooth, lubricious surface quality offers low sliding resistance.

Typical applications include jigs, fixtures and other forms of general manufacturing tooling, and is particularly effective for applications needing a non-marring interface between the tool and the workpiece.

## Contents:

Overview .....	2
Ordering Information .....	3
Physical Properties .....	4
Mechanical Properties .....	5
Appendix .....	7

## Ordering Information

**3D Printer Compatibility:** F370™

**Support Material:** SUP4000B™

**Build Tray:** F370, High Temperature

**Table 1. Diran 410MF07 Thermoplastic Filament Ordering Information**

Part Number	Description
<b>Filament Canisters</b>	
333-90410	Diran 410MF07, 90 cu in, F123
333-60400	SUP4000B™, 60 cu in, F123
<b>Printer Consumables</b>	
123-00401-S	F370 Extrusion Head
123-00314-S	F370 Build Tray, High Temperature

## Physical Properties

Values are measured as printed. XY and XZ/ZX orientations were tested.

For full details refer to the [Stratasys Materials Test Procedure on www.stratasys.com](http://www.stratasys.com).

DSC and TMA curves can be found in the Appendix.

**Table 2. Diran 410MF07 Thermoplastic Filament Physical Properties**

Property	Test Method	Typical Values XY	Typical Values XZ/ZX
HDT @ 66psi	ASTM D648 Method B	90 °C (194 °F)	90 °C (194 °F)
HDT @ 264psi	ASTM D648 Method B	70 °C (158 °F)	70 °C (158 °F)
Tg	ASTM D7426 Inflection Point	117.34 °C (243.21 °F)	117.34 °C (243.21 °F)
Mean CTE	ASTM E831 (40 °C to 140 °C)	56.60 $\mu\text{m}/[\text{m}\cdot^{\circ}\text{C}]$ (31.44 $\mu\text{in}/[\text{in}\cdot^{\circ}\text{F}]$ )	112.6 $\mu\text{m}/[\text{m}\cdot^{\circ}\text{C}]$ (62.56 $\mu\text{in}/[\text{in}\cdot^{\circ}\text{F}]$ )
Volume Resistivity	ASTM D257	$1.50 \cdot 10^{15} \Omega\text{-cm}$	$1.50 \cdot 10^{15} \Omega\text{-cm}$
Dielectric Constant	ASTM D150 1 kHz test condition	3.58	3.73
Dielectric Constant	ASTM D150 2 MHz test condition	2.85	2.95
Dissipation Factor	ASTM D150 1 kHz test condition	0.013	0.014
Dissipation Factor	ASTM D150 2 MHz test condition	0.000	0.012
Specific Gravity	ASTM D792 @ 23 °C	1.16	1.16


# Mechanical Properties

Samples were printed with 0.010 in. (0.254 mm) layer height.

For the full test procedure please see the Stratasys Materials Test Procedure on [www.stratasys.com](http://www.stratasys.com).


## Print Orientation

Parts created using FDM are anisotropic as a result of the printing process. Below is a reference of the different orientations used to characterize the material.

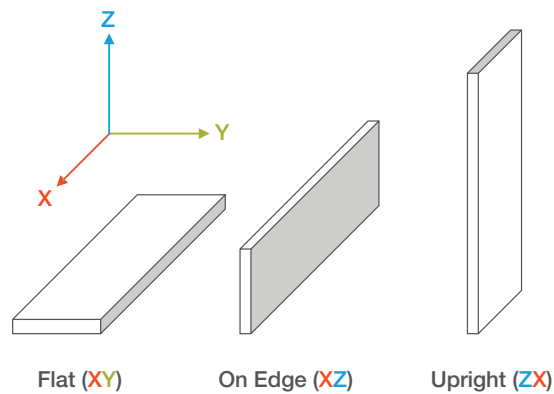

## Tensile Curves

Due to the anisotropic nature of FDM, tensile curves look different depending on orientation. Below is a guide of the two types of curves seen when printing tensile samples and what reported values mean.

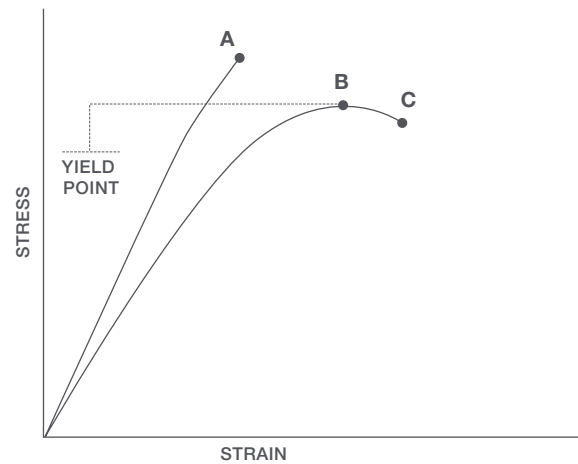

**A** = Tensile at break, elongation at break (no yield point)

**B** = Tensile at yield, elongation at yield

**C** = Tensile at break, elongation at break

**Table 3. Diran 410MF07 Thermoplastic Filament Mechanical Properties**

		XZ Orientation <sup>(1)</sup>	ZX Orientation <sup>(1)</sup>
<b>Tensile Properties: ASTM D638</b>			
Yield Strength	MPa	44.8 (1.5)	No Yield
	psi	6490 (220)	No Yield
Elongation @ Yield	%	4.3 (0.041)	No yield
Strength @ Break	MPa	40.4 (3.0)	30.7 (2.0)
	psi	5860 (440)	4460 (290)
Elongation @ Break	%	12 (3.2)	3.1 (1.0)
Modulus (Elastic)	GPa	1.69 (0.017)	1.46 (0.021)
	ksi	246 (2.4)	212 (3.0)
<b>Flexural Properties: ASTM D790, Procedure A</b>			
Strength @ Break	MPa	No break	46.7 (2.3)
	psi	No break	6770 (330)
Strength @ 5% Strain	MPa	59.9 (1.6)	-
	psi	8690 (230)	-
Strain @ Break	%	No break	3.1 (0.53)
Modulus	GPa	1.85 (0.043)	1.47 (0.065)
	ksi	268 (6.2)	213 (9.4)
<b>Compression Properties: ASTM D695</b>			
Yield Strength	MPa	75.8 (4.3)	163 (30)
	psi	11000 (630)	23600 (4300)
Modulus	GPa	1.54 (0.026)	1.46 (0.022)
	ksi	223 (3.8)	212 (3.2)
<b>Impact Properties: ASTM D256, ASTM D4812</b>			
Izod, Notched	J/m	442 (76)	26.8 (5.3)
	ft*lb/in	8.28 (1.4)	0.502 (0.10)
Izod, Unnotched	J/m	1420 (200)	142 (25)
	ft*lb/in	26.5 (3.8)	2.66 (0.46)

(1) Values in parentheses are standard deviations

# Appendix

Figure 1. 2nd heating scan, DSC, for Diran 410MF07

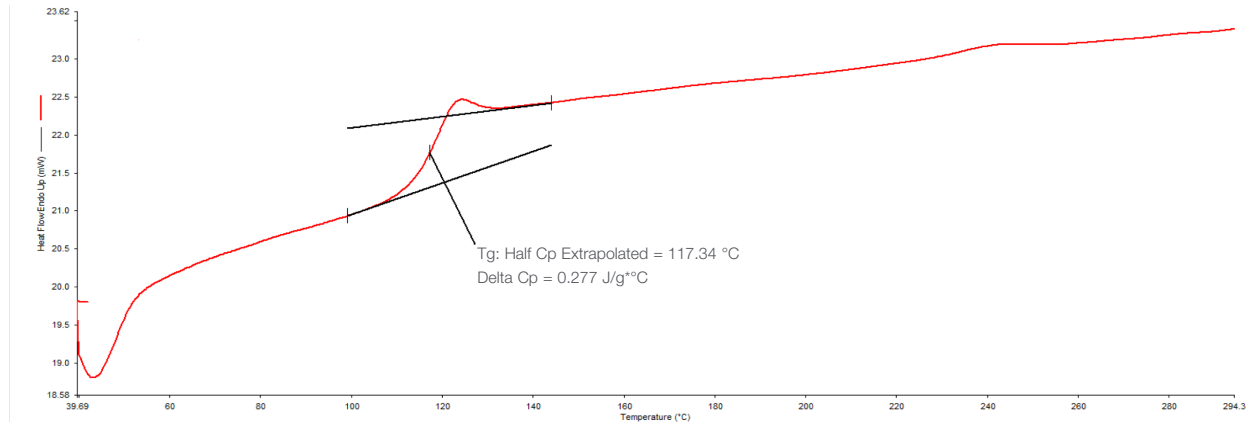


Figure 2. TMA CTE curve inplane with the layer

Sample: Flat-1  
 Size: 6.3338 mm  
 Method: Ramp  
 Comment: RT-160C @ 3C/min

## TMA


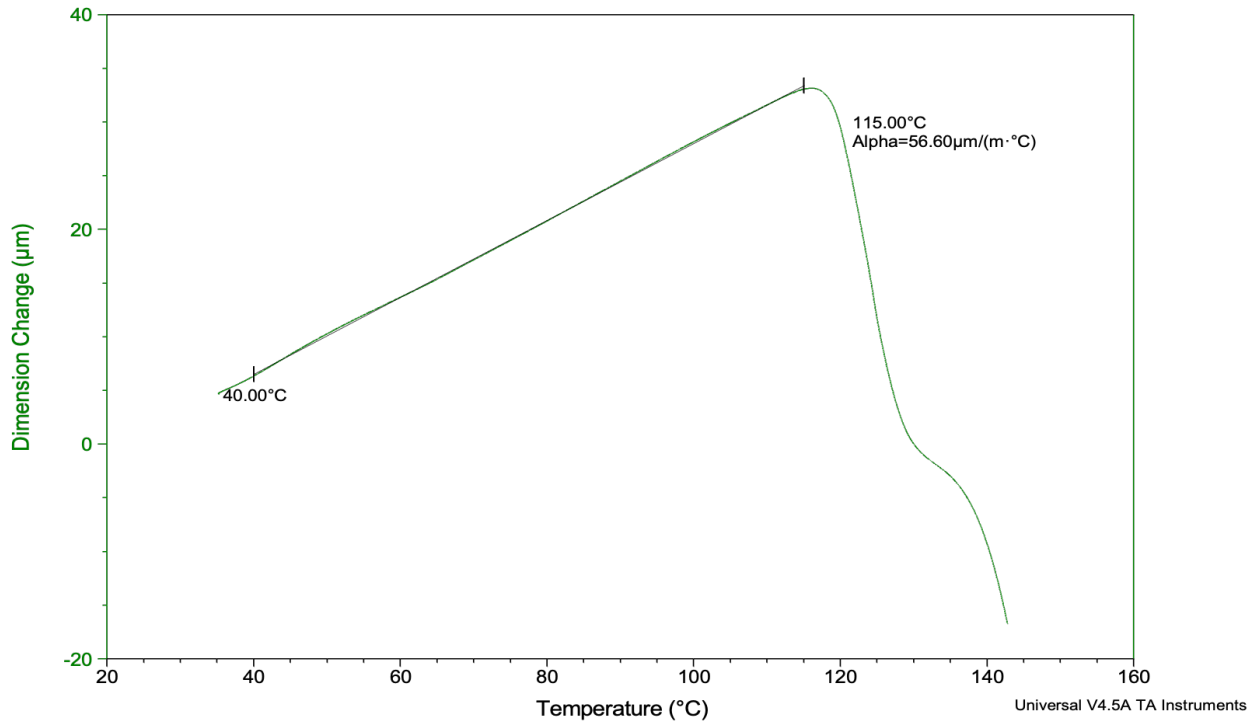


Figure 3. TMA CTE curve normal to the layer

Sample: Side-1  
 Size: 6.4269 mm  
 Method: Ramp  
 Comment: RT-160C @ 3C/min

### TMA

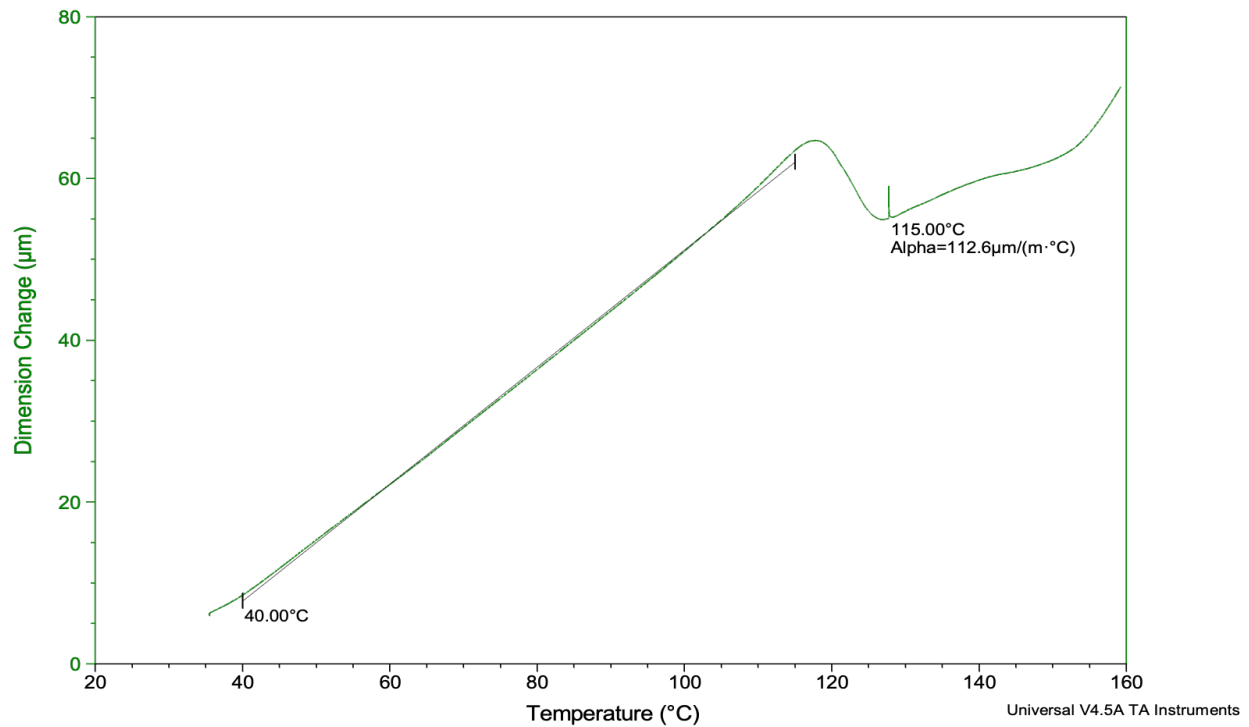

#### Stratasys Headquarters

7665 Commerce Way,  
 Eden Prairie, MN 55344  
 +1 800 801 6491 (US Toll Free)  
 +1 952 937-3000 (Intl)  
 +1 952 937-0070 (Fax)

1 Holtzman St., Science Park,  
 PO Box 2496  
 Rehovot 76124, Israel  
 +972 74 745 4000  
 +972 74 745 5000 (Fax)

[stratasys.com](http://stratasys.com)

ISO 9001:2015 Certified

